

Attractive forces in microporous carbon electrodes for capacitive deionization

P. M. Biesheuvel · S. Porada · M. Levi · M. Z. Bazant

Received: 8 July 2013 / Revised: 14 December 2013 / Accepted: 9 January 2014 / Published online: 1 February 2014
© Springer-Verlag Berlin Heidelberg 2014

Abstract The recently developed modified Donnan (mD) model provides a simple and useful description of the electrical double layer in microporous carbon electrodes, suitable for incorporation in porous electrode theory. By postulating an attractive excess chemical potential for each ion in the micropores that is inversely proportional to the total ion concentration, we show that experimental data for capacitive deionization (CDI) can be accurately predicted over a wide range of applied voltages and salt concentrations. Since the ion spacing and Bjerrum length are each comparable to the micropore size (few nanometers), we postulate that the attraction results from fluctuating bare Coulomb interactions between individual ions and the metallic pore surfaces (image forces) that are not captured by mean-field theories, such as the Poisson-

Boltzmann-Stern model or its mathematical limit for overlapping double layers, the Donnan model. Using reasonable estimates of the micropore permittivity and mean size (and no other fitting parameters), we propose a simple theory that predicts the attractive chemical potential inferred from experiments. As additional evidence for attractive forces, we present data for salt adsorption in uncharged microporous carbons, also predicted by the theory.

Introduction

Electrodes made of porous carbons can be utilized to desalinate water in a technique called capacitive deionization (CDI) in which a cell is constructed by placing two porous carbon electrodes parallel to one another [1–12]. A cell voltage difference is applied between the electrodes, leading to an electrical and ionic current in the direction from one electrode to the other. The water flowing through the cell is partially desalinated because ions are adsorbed in their respective counterelectrode. CDI is, in essence, a purely capacitive process, based on the storage (electrosorption) of ions in the electrical double layer (EDL) that forms within the electrolyte-filled micropores of the carbon upon applying a cell voltage (the measurable voltage difference applied between an anode and a cathode). In CDI, the cathode (anode) is defined as the electrode that adsorbs the cations (anions) during the desalination step. Note that while counterions are adsorbed, co-ions are expelled from the EDLs, leading to a diminished desalination and a charge efficiency Λ lower than unity [13–20]. The charge efficiency Λ is defined for a 1:1 salt solution (NaCl) as the ratio of salt adsorption by a CDI electrode cell pair, divided by the charge stored in an electrode. It is typically defined for a cycle where the salt adsorption step is long enough for an equilibrium to be

P. M. Biesheuvel · S. Porada
Wetsus, Centre of Excellence for Sustainable Water Technology,
Agora 1, 8934 CJ Leeuwarden, The Netherlands

P. M. Biesheuvel
Laboratory of Physical Chemistry and Colloid Science, Wageningen
University, Dreijenplein 6, 6703 HB Wageningen, The Netherlands

P. M. Biesheuvel (✉)
Department of Environmental Technology, Wageningen University,
Bornse Weilanden 9, 6708 WG Wageningen, The Netherlands
e-mail: maarten.biesheuvel@wur.nl

M. Levi
Department of Chemistry, Bar-Ilan University, Ramat-Gan 52900,
Israel

M. Z. Bazant
Department of Chemical Engineering, Massachusetts Institute of
Technology, Cambridge, MA 02139, USA

M. Z. Bazant
Department of Mathematics, Massachusetts Institute of Technology,
Cambridge, MA 02139, USA

reached [21]. Charge efficiency describes the ratio of salt adsorption over charge, for a cycle where the cell voltage V_{cell} is switched periodically between two values, with the high value applied during salt adsorption and the low value during salt desorption. The low cell voltage is most often $V_{\text{cell}}=0$ V, applied simply by electrically short-circuiting the two cells during the salt desorption step. As we will demonstrate in this work, the charge efficiency Λ is a very powerful concept to test the suitability of EDL models proposed for ion adsorption in electrified materials.

In a porous carbon material where pores are electrolyte-filled, the surface charge is screened by the adsorption of counterions and by the desorption of co-ions. The ratio between counterion adsorption and co-ion desorption depends on the surface charge. At low surface charge, the ratio is 1, since for each pair of electrons transferred to a carbon particle, one cation is adsorbed and one anion is expelled, a phenomenon called “ion swapping” by Wu et al. [22]. This local conservation of the total ion density is a general feature of the linear response of an electrolyte to an applied voltage smaller than the thermal voltage [23–25]. When in the opposite electrode the same occurs, the charge efficiency Λ of the electrode pair will be zero: there is no net salt adsorption from the electrolyte solution flowing in between the two electrodes. In the opposite extreme of a very high surface charge, we approach the limit where counterion adsorption is responsible for 100 % of the charge screening, and we come closer to the limit of $\Lambda=1$, where for each electron transferred between the electrodes, one salt molecule is removed from the solution flowing in between the electrodes [7]. This regime exemplifies the strongly nonlinear response of an electrolyte to a large voltage that greatly exceeds the thermal voltage [23, 24]. Correct prediction of the charge efficiency is one requirement of a suitable EDL model.

Contrary to what has often been reported over the past decades [2, 26–32], it is not the mesopores (2–50 nm), but the micropores (<2 nm) that are the most effective in achieving a high desalination capacity by CDI [33, 34]. Interestingly, already in 1999, based on capacitance measurements in 30 % H_2SO_4 solutions, Lin et al. [35] identified the pore range 0.8–2 nm as the optimum size for EDL formation. The microporous activated carbon MSP-20 (micropore volume 0.96 mL/g, 98 % of all pores are microporous) has the highest reported desalination capacity of 16.8 mg/g (per gram of active material), when tested at 5 mM NaCl and a 1.2-V cell voltage [34, 36]. In these micropores, typically, the Debye length λ_D will be of the order of, or larger than, the pore size. In water at room temperature, the length scale λ_D (in nanometers) can be approximated by $\lambda_D \sim 10/\sqrt{c_\infty}$ with c_∞ the salt concentration in mM. This implies that the Debye length is around $\lambda_D \sim 3$ nm for $c_\infty=10$ mM. Note that the Debye length is not based on the salt concentration within the EDL, but on the salt concentration c_∞ outside the region of EDL overlap, thus in

the interparticle pores outside the carbon particles. Because of the high ratio of the Debye length over the pore size, in constructing a simple EDL model, it is a good approach for such microporous materials to assume full overlap of the two diffuse Gouy-Chapman layers [19, 37] extending from each side of the pore, leading to an EDL model based on the Donnan concept, in which the electrical potential makes a distinct jump from a value in the space outside the carbon particles to another value within the carbon micropores, without a further dependence of potential on the exact distance to the carbon walls; see Fig. 1b [21, 25, 38–41]. The Donnan approximation is the mathematical limit of the mean-field Poisson-Boltzmann (PB) theory for overlapping diffuse double layers, when the Debye length greatly exceeds pore size. In this limit, the exact pore geometry is no longer of importance in the PB theory, and neither is the surface area. Instead, only the pore volume matters. As an example of the validity of the Donnan model, for a slit-shaped pore with 1 M of volumetric charge density and for an external salt concentration of $c_\infty=10$ mM, for any pore size below 10 nm, the charge efficiency Λ according to the PB equation is ~ 0.98 , in exact agreement with the Donnan model. Similar Donnan concepts are used in the field of membrane science [42, 43], polyelectrolyte theory [44, 45], and colloidal sedimentation [46, 47].

To describe experimental data for desalination in CDI, the simplest Donnan approach, where only the jump in potential from the outside to inside the pore is considered, must be extended in two ways. First of all, an additional capacitance must be included which is located between the ionic diffuse charge and the electronic charge in the carbon. This capacitance may be due to a voltage drop within the carbon itself (space charge layer or quantum capacitance) [48]. Another reason can be the fact that the ionic charge and electronic charge cannot come infinitely close, e.g., due to the finite ion size, and a dielectric layer of atomic dimension is located in between, called the Stern layer; see Fig. 1. In this work, we describe this additional capacitance using the Stern layer-concept. Secondly, to describe data, it was found necessary to include an excess chemical potential, $-\mu_{\text{att}}$, that describes an additional attraction of each ion to the micropore. This attraction may result from chemical effects [49, 50], but we propose below a quantitative theory based on electrostatic image forces [51, 52], not captured by the classical mean-field approximation of the Donnan model.

Because of its mathematical simplicity, this modified Donnan (mD) model is readily included in a full 1D or 2D porous electrode theory and therefore not only describes the equilibrium EDL structure, but can also be used in a model for the dynamics of CDI [37, 40, 53–55]. Despite this success, it was found that the mD model is problematic when describing simultaneously multiple datasets in a range of values of the external salt concentration. Even when data at just two salt concentrations are simultaneously considered, such as for

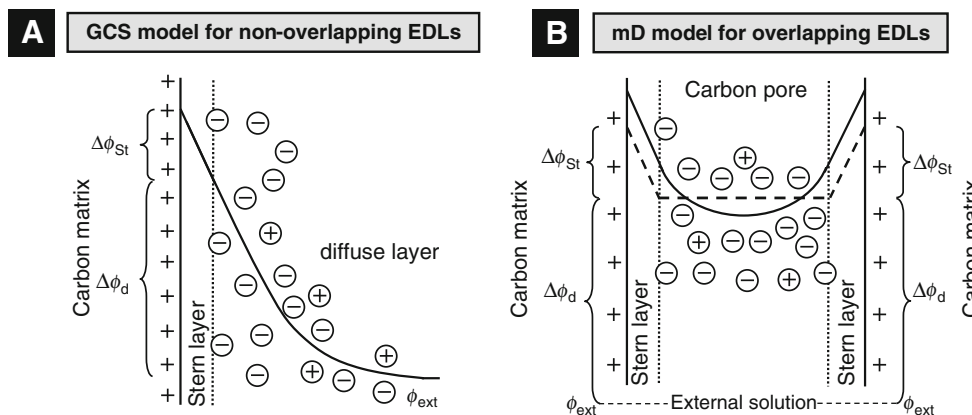


Fig. 1 Schematic view of electrical double layer models used for microporous carbon electrodes. *Solid and dashed lines* sketch the potential profile and, outside the Stern layers, also indicate the profile of counterion concentration. **a** Gouy-Chapman-Stern theory for a planar wall without electrical double layer (EDL) overlap. The intersection of Stern layer and diffuse layer is the Stern plane, or outer Helmholtz plane.

b Modified Donnan model. The strong overlap of the diffuse layers (*solid line*) results in a fairly constant value of diffuse layer potential and ion concentration across the pore (unvarying with pore position), the more so the smaller the pores. In the Donnan model, this potential and the ion concentrations are set to a constant value (*horizontal dashed line*)

NaCl solutions with 5 and 20 mM of salt concentration, it was problematic for the mD model to describe both datasets accurately. Extending the measurement range to 100 mM and beyond, these problems aggravate; see the mismatch between data and theory in Fig. 3 in ref. [38]. We ascribe this problem to the constancy of μ_{att} in the standard version of the mD model. One extreme consequence of this assumption is that the model predicts unrealistically high salt adsorptions when uncharged carbon is contacted with water of seawater concentration (~0.5 M), e.g., for a typical value of $\mu_{att}=2.0$ kT and $c_{\infty}=0.5$ M, it predicts an excess salt concentration in uncharged carbons of 3.19 M (with the excess ion concentration twice this value), which is very unrealistic.

In this manuscript, we present a physical theory of electrical double layers (EDLs) in microporous carbon electrodes that explains why μ_{att} is not a constant but in effect decreases at increasing values of micropore total ion concentration. In this way, the spurious effect of the prediction of a very high salt adsorption of carbons brought in contact with seawater is avoided. The “Theory” section describes the theory together with the implementation of the mD model for CDI. In the “Results and discussion” section, we collect various published datasets of CDI using commercial film electrodes based on activated carbon powders and fit the data with a simple equation for μ_{att} inversely dependent on the micropore ion concentration, consistent with our model of image forces. This is a simple theory that has the advantage over more comprehensive and detailed EDL models [22, 56–64] that it can be readily included in a full porous electrode transport theory. Now that μ_{att} is no longer a constant but a function of the total ion concentration in the pore, which via the Boltzmann relation depends on μ_{att} , a coupled set of algebraic equations results to describe charge and salt adsorption in the micropores of porous carbons. We will demonstrate that across many

datasets, this modification improves the predictive power of the mD model very substantially, without predicting extreme salt adsorption at high salinity anymore.

Theory

General description of modified Donnan model

To describe the structure of the EDL in microporous carbons, the mD model can be used, which relates the ion concentrations inside carbon particles (in the intraparticle pore space, or micropores, “mi”) to the concentration outside the carbon particles (interparticle pore space, or macropores) [65, 66]. At equilibrium, there is no transport across the electrode, and the macropore concentration is equal to that of the external solution outside the porous electrode, which we will describe using the subscript “ ∞ ”.

In general, in the mD model, the micropore ion concentration relates to that outside the pores according to the Boltzmann equilibrium:

$$c_{mi,i} = c_{\infty,i} \cdot \exp(-z_i \cdot \Delta\phi_d + \mu_{att,i}) \tag{1}$$

where z_i is the valency of the ion, and $\Delta\phi_d$ the Donnan potential, i.e., the potential increase when going from outside to inside the carbon pore. This is a dimensionless number and can be multiplied by the thermal voltage $V_T=RT/F$ to obtain the Donnan voltage with dimension V .

The Donnan voltage is a potential of mean force derived from the Poisson-Boltzmann mean-field theory, which assumes that the electric field felt by individual ions is generated self-consistently by the local mean charge density. Therefore, the excess chemical potential of each ion, $-\mu_{att}$, has a

contribution from electrostatic correlations, which is generally attractive if dominated by image forces in a metallic micropore, as described below. We use μ_{att} as a dimensionless number which can be multiplied by kT to obtain an energy per ion with dimension J .

In the mD model, we consider that outside the carbon particles, there is charge neutrality

$$\sum_i z_i \cdot c_{\infty,i} = 0, \quad (2)$$

while inside the carbon micropores, the micropore ionic charge density (per unit micropore volume, dimension $\text{mol}/\text{m}^3 = \text{mM}$) is given by

$$\sigma_{\text{mi}} = \sum_i z_i \cdot c_{\text{mi},i}. \quad (3)$$

This ionic charge is compensated by the electronic charge in the carbon matrix: $\sigma_{\text{mi}} = -\sigma_{\text{elec}}$. In using this simple equation, we explicitly exclude the possibility of chemical surface charge effects, but such an effect can be included [54]. Equation 3 describes local electroneutrality in the micropores, a well-known concept frequently used in other fields as well, such as in polyelectrolyte theory [44, 45], ion-exchange membranes [42, 43], and colloidal sedimentation [46, 47]. The ionic charge density relates to the Stern layer potential difference, $\Delta\phi_{\text{St}}$ according to

$$\sigma_{\text{mi}} = -C_{\text{St},\text{vol}} \cdot \Delta\phi_{\text{St}} \cdot V_T \cdot F \quad (4)$$

where $C_{\text{St},\text{vol}}$ is a volumetric Stern layer capacity in farads per cubic meter. For $C_{\text{St},\text{vol}}$, we use the expression

$$C_{\text{St},\text{vol}} = C_{\text{St},\text{vol},0} + \alpha \cdot \sigma_{\text{mi}}^2 \quad (5)$$

where the second term empirically describes the experimental observation that the Stern layer capacity goes up with micropore charge, where α is a factor determined by fitting the model to the data [33, 67–69]. To consider a full cell, we must add to Eqs. 1–5 (evaluated for both electrodes) the fact that the applied cell voltage relates to the EDL voltages in each electrode according to

$$V_{\text{cell}} - V_T = |\Delta\phi_{\text{d}} + \Delta\phi_{\text{St}}|_{\text{cathode}} + |\Delta\phi_{\text{d}} + \Delta\phi_{\text{St}}|_{\text{anode}}. \quad (6)$$

Allowing for unequal electrode mass, we have as an additional constraint that the electronic charge in one electrode plus that in the other, sum up to zero,

$$\sigma_{\text{mi},\text{cathode}} \cdot \text{mCmA} = -\sigma_{\text{elec},\text{cathode}} \cdot \text{mCmA} = \sigma_{\text{elec},\text{anode}} = -\sigma_{\text{mi},\text{anode}} \quad (7)$$

where mCmA is the mass ratio cathode to anode. In an adsorption/desorption cycle, the adsorption of a certain ion i by the cell pair, per gram of both electrodes combined, is given by [39]

$$\Gamma_i = v_{\text{mi}} \cdot \left[\frac{\text{mCmA}}{\text{mCmA} + 1} \cdot (c_{\text{mi},i}^{\text{cathode}} - c_{\text{mi},i}^0) + \frac{1}{\text{mCmA} + 1} \cdot (c_{\text{mi},i}^{\text{anode}} - c_{\text{mi},i}^0) \right] \quad (8)$$

where superscript “0” refers to the discharge step, when typically a zero cell voltage is applied between an anode and cathode. In Eq. 8, v_{mi} is the micropore volume per gram of electrode which in an electrode film is the product of the mass fraction of porous carbon in an electrode, e.g., 0.85, and the pore volume per gram of carbon, as measured, for instance, by N_2 adsorption analysis. The question of which pore volume to use (i.e., based on which pore size range) is an intricate question addressed in ref. [34].

This set of equations describes the mD model for general mixtures of ions and includes the possibility of unequal electrode masses (e.g., a larger anode than cathode) and unequal values for μ_{att} for the different ions. For the specific case of a 1:1 salt as NaCl, the cation adsorption equals the anion adsorption, and thus Eq. 8 also describes the salt adsorption, Γ_{salt} , in a cycle. The charge per gram of both electrodes Σ is given by $\Sigma = v_{\text{mi}} / (\text{mCmA} + 1) \cdot (\sigma_{\text{mi}}^{\text{anode}} - \sigma_{\text{mi}}^{\text{anode},0})$. The ratio of these two numbers is the charge efficiency of a CDI cycle, Λ ; see Fig. 5 for various values of mCmA.

Equal electrode mass

Next, we limit ourselves to the case that there is an equal mass of anode and cathode, i.e., the two electrodes are the same, and thus $\sigma_{\text{elec},\text{cathode}} + \sigma_{\text{elec},\text{anode}} = 0$. After solving Eqs. 1–5 for each electrode separately, together with Eq. 6, we can calculate the electrode charge and salt adsorption by the cell.

Multiplying micropore charge density σ_{mi} (for which we can take any of the values considered in Eq. 7, ionic or electronic, in the anode or in the cathode, as they are all the same when mCmA=1) by Faraday’s constant, F , and by the volume of micropores per gram of electrode, v_{mi} , we obtain for the charge Σ_F in coulombs per gram,

$$\Sigma_F = \frac{1}{2} \cdot F \cdot v_{\text{mi}} \cdot |\sigma_{\text{mi}} - \sigma_{\text{mi}}^0| \quad (9)$$

and for the ion adsorption of a cell pair,

$$\Gamma_i = \frac{1}{2} \cdot v_{\text{mi}} \cdot (c_{\text{mi},i}^{\text{cathode}} - c_{\text{mi},i}^{\text{cathode},0} + c_{\text{mi},i}^{\text{anode}} - c_{\text{mi},i}^{\text{anode},0}). \quad (10)$$

In case that the cell voltage is set to zero during discharge, then (without chemical charge on the carbon walls) $\sigma_{\text{mi},i}^0 = 0$ and $c_{\text{mi},i}^{\text{cathode},0} = c_{\text{mi},i}^{\text{anode},0} = c_{\text{mi},i}^0$.

Monovalent salt solution—equal electrode mass

Next, we focus on a 1:1 salt such as NaCl, in addition to assuming that the two electrodes have the same mass. In the case of a 1:1 salt, $c_{\infty, \text{cation}}$ is equal to $c_{\infty, \text{anion}}$, and we can equate both to the external salt concentration, c_{∞} . From this point onward, we will assume μ_{att} to be the same for Na^+ as Cl^- (see note 1 at the end of manuscript). For a 1:1 single-salt solution, combination of Eqs. 1–5 leads to

$$\sigma_{\text{mi}} = c_{\text{cation,mi}} - c_{\text{anion,mi}} = -2 \cdot c_{\infty} \cdot \exp(\mu_{\text{att}}) \cdot \sinh(\Delta\phi_{\text{d}}) \quad (11)$$

and

$$c_{\text{ions,mi}} = c_{\text{cation,mi}} + c_{\text{anion,mi}} = 2 \cdot c_{\infty} \cdot \exp(\mu_{\text{att}}) \cdot \cosh(\Delta\phi_{\text{d}}). \quad (12)$$

Because of symmetry, in this situation, Eq. 6 simplifies to

$$V_{\text{cell}} - V_{\text{T}} = 2 \cdot |\Delta\phi_{\text{d}} + \Delta\phi_{\text{St}}|, \quad (13)$$

while only one electrode needs to be considered. For a 1:1 salt, the amount of anion adsorption by the cell pair equals the amount of cation adsorption, and thus $\Gamma_{\text{cation}} = \Gamma_{\text{anion}} = \Gamma_{\text{salt}}$.

The charge efficiency, being the measurable equilibrium ratio of salt adsorption Γ_{salt} over charge Σ is now given by (clearly defined as an integral quantity)

$$\Lambda = \frac{\Gamma_{\text{salt}}}{\Sigma} = \frac{c_{\text{ions,mi}} - c_{\text{ions,mi}}^0}{|\sigma_{\text{mi}}|} = \tanh\left(\frac{|\Delta\phi_{\text{d}}|}{2}\right) \quad (14)$$

in case that (1) the reference condition (condition during ion desorption step) is a zero cell voltage, and (2) we use the single-pass method of testing, where the salt concentration c_{∞} is the same before and after applying the voltage. Note that this condition does not apply when the batch mode of CDI testing is used where c_{∞} is different between the end of the charging and the end of the discharging step (see ref. [7]). In Eq. 14, the charge Σ , expressed in moles per gram, is equal to Σ_F divided by F . Equation 14 demonstrates that Λ is not directly dependent of such parameters as μ_{att} , $C_{\text{St,vol}}$, or c_{∞} , but solely depends on $\Delta\phi_{\text{d}}$ [16, 23]. Of course, in an experiment with a certain applied cell voltage, all of these parameters do play a role in determining the value of Λ via their influence on $\Delta\phi_{\text{d}}$. An equation similar to Eq. 14 is given in the context of ion transport through lipid bilayers as Eqs. 8 and 10 in ref. [70].

Simple theory of image forces in micropores

Here, we propose a first approximation of μ_{att} due to image forces between individual ions in the micropores and the metallic carbon matrix [71], leading to a simple formula that provides an excellent description of our experimental data

below. Image forces have been described with discrete dipole models for counterion-image monolayers [52], as well as (relatively complicated) extensions of Poisson-Boltzmann theory [51]. Simple modified Poisson equations that account for ion-ion Coulomb correlations that lead to charge oscillations in single component plasmas [72, 73] and multicomponent electrolytes or ionic liquids [74] are beginning to be developed, but image forces at metallic or dielectric surfaces have not yet been included. Moreover, to our knowledge, image forces have never been included in any mathematical model for the dynamics of an electrochemical system.

Consider a micropore of size $\lambda_p \approx 1-5$ nm whose effective permittivity, ϵ_p , is smaller than that of the bulk electrolyte, ϵ_b , due to water confinement and the dielectric decrements of solvated ions. The local Bjerrum length in the micropore

$$\lambda_B = \frac{e^2}{4\pi\epsilon_p kT} \quad (15)$$

is larger than its bulk value ($\lambda_B = 0.7$ nm in water at room temperature) by a factor of $\epsilon_b/\epsilon_p \approx 5-10$ and thus is comparable to the pore size. As such, ions have strong attractive Coulomb interactions $-E_{\text{im}} > kT$ with their image charges from anywhere within the micropore. For a spherical metallic micropore of radius λ_p , the image of an ion of charge $q = \pm ze$ at radial position r has charge $q = \mp \lambda_p q/r$ and radial position $r = \lambda_p^2/r$ outside the pore [75]; see Fig. 2. The attractive Coulomb energy between the ion and its image,

$$E_{\text{im}}(r) = \frac{\lambda_p (ze)^2}{4\pi\epsilon_p (\lambda_p^2 - r^2)} \quad (16)$$

diverges at the surface, $r \rightarrow \lambda_p$, but the Stern layer of solvation keeps the ions far enough away to prevent specific adsorption. For consistency with the Donnan model, which assumes constant electrochemical potentials within the micropores (outside the Stern layers), we approximate the image attraction

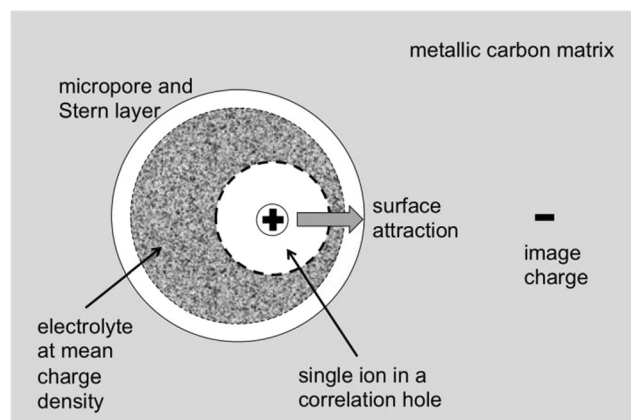


Fig. 2 Sketch of electrostatic image correlations leading to attractive surface forces for all ions in a micropore, whose size is comparable to both the Bjerrum length and the mean ion spacing

energy by a constant, equal to its value at the center of the micropore:

$$E_{\text{im}} \approx \frac{(ze)^2}{4\pi\epsilon_p\lambda_p} = z^2 kT \cdot \frac{\lambda_B}{\lambda_p} \quad (17)$$

This scaling is general and also holds for other geometries, such as parallel-plate or cylindrical pores, with a suitable redefinition of λ_p . The image force on a given ion is significantly reduced by the presence of other ions due to Coulomb correlations, which effectively converts the bare ion monopole into collections of fluctuating multipoles with more quickly decaying electric fields. The attractive excess chemical potential, $\mu_{\text{att}} = E_{\text{im}} P_{\text{im}}$, is thus multiplied by the probability that an ion falls into a “correlation hole,” or fluctuating empty region, and feels a bare image force. If the mean volume of a correlation hole, $c_{\text{ions,mi}}^{-1}$, is smaller than the characteristic pore volume, λ_p^3 , then the probability that a given particle enters a correlation hole scales as $P_{\text{im}} \approx (\lambda_p^3 c_{\text{ions,mi}})^{-1}$. This implies that the excess chemical potential due to image forces is inversely proportional to the *total* concentration of all ions, since the image energy is independent of the sign of the charge.

We thus arrive at a very simple formula for the excess attractive chemical potential

$$\mu_{\text{att}} = \frac{E}{c_{\text{ions,mi}}} \quad (18)$$

where

$$E = z^2 \cdot kT \cdot \lambda_B \cdot \lambda_p^{-4} \quad (19)$$

Results and discussion

In the next sections, we present a reanalysis of three sets of data of water desalination by CDI using commercial composite carbon film electrodes. These data were previously compared with the standard mD model (that assumes μ_{att} to be a constant). Here, we will demonstrate how making μ_{att} a simple function of $c_{\text{ions,mi}}$ according to Eq. 18 significantly improves the fit to the data, without extra fitting parameters. We call this the improved mD model. In the last section we analyse experiments of salt adsorption in uncharged carbon to have direct access to the energy parameters E and μ_{att}

and also include ion and pore wall volume effects by using a modified Carnahan-Starling equation of state.

In all sections, the same parameter settings are used, being $p_{\text{mi}} = 0.30$ and $\rho_{\text{elec}} = 0.55$ g/mL, thus $v_{\text{mi}} = p_{\text{mi}}/\rho_{\text{elec}} = 0.545$ mL/g, $C_{\text{St,vol,0}} = 0.145$ GF/m³, $\alpha = 30$ F m³/mol², $E = 300$ kT mol/m³. The carbon electrodes are based on a commercial material provided by Voltea B.V. (Sassenheim, The Netherlands) which contained activated carbon, polymer binder, and carbon black. This material was used in all our studies in refs. [21, 25, 38, 39, 76, 77].


Data for varying cell voltage at two values of salt concentration (5 and 20 mM NaCl)

Data for charge and salt adsorption by a symmetric pair of activated carbon electrodes as a function of salt concentration (5 and 20 mM NaCl) and cell voltage was presented in ref. [16] and was reanalyzed using the standard mD model in ref. [38]. By “standard” we imply using a fixed value of μ_{att} . Though a reasonable good fit was obtained (see Fig. 2b in ref. [38]), the effect of salinity c_∞ was overestimated.

To describe in more detail how well the standard mD model fits the data, we make the following analysis: As Eq. 11 demonstrates, according to the standard mD approach, there is a direct relationship between the ratio $\sigma_{\text{mi}}/c_\infty$ and $\Delta\phi_d$, and thus, according to Eq. 14, there is also a direct relationship between $\sigma_{\text{mi}}/c_\infty$ and Λ . Thus, two datasets (each for a range of cell voltages) obtained at two values of the external salinity, c_∞ , should overlap. However, as Fig. 3a demonstrates, the two datasets do not, and they stay well separated. This is direct evidence that the standard mD model with a fixed μ_{att} is not accurate enough. A direct check whether a modified mD model works better is to plot the two datasets together with the corresponding two modeling lines (thus for two values of c_∞), all in one graph, and choose such an x -axis parameter that the modeling lines overlap and check if now the two datasets overlap better. This procedure is followed in Fig. 3b where it is clearly observed that when we plot Λ vs. $\sigma_{\text{mi}}/(c_\infty/c_{\text{ref}})^a$ with $c_{\text{ref}} = 20$ mM and the power a equal to $a = 0.31$, the modeling lines for the improved mD model collapse on top of one another, and also the data now almost perfectly overlap. Note that the value of $a = 0.31$ has no special significance as far as we know; it is just a chosen value to make the modeling lines overlap. Clearly, the use of the improved mD model to describe μ_{att} as a function of $c_{\text{ions,mi}}$ results in a significantly better fit of the model to the data.

Figure 3c plots the total ion concentration in the micropore volume vs. the micropore charge. In this representation, we observe again a good fit of the improved mD model to the data. Note that the modeling fit in Fig. 3b, c is independent of details of the Stern layer (see Eq. 5) and only depends on the

Fig. 3 Analysis of data of salt adsorption and charge efficiency Λ for NaCl solutions at $c_\infty=5$ and 20 mM for cell voltages up to $V_{\text{cell}}=1.4$ V. **a** Plotting Λ vs. the ratio $\sigma_{\text{mi}}/c_\infty$ does not lead to overlap of the datasets, demonstrating that using $\mu_{\text{att}}=\text{constant}$ in the standard mD model is not correct. **b** Plotting Λ vs. $\sigma_{\text{mi}} \cdot (c_{\text{ref}}/c_\infty)^a$ with $a=0.31$ leads to a perfect overlap of the modeling lines, where $\mu_{\text{att}}=E/c_{\text{ions,mi}}$ and $E=300$ kT mol/m³. The datasets now also overlap quite closely demonstrating the relevance of the use of the improved mD model ($c_{\text{ref}}=20$ mM). **c** Using the improved mD model, the total excess micropore ion adsorption, $c_{\text{ions,mi}}$ (equal to salt adsorption in a symmetric cell pair), is plotted vs. the micropore charge density, σ_{mi} , showing the expected deviation from the 100 % charge efficiency line. **d** Theory of Λ vs. V_{cell} according to the improved mD model (compared with data), showing a much smaller influence of c_∞ on Λ than in the standard mD model; see Fig. 2b in ref. [38]. **e–g** Direct data of salt adsorption Γ_{salt} in milligrams per gram and charge Σ_F in coulombs per gram, compared with the improved mD model. **h** Calculated micropore ion concentrations as a function of electrode charge, again compared with the improved mD model

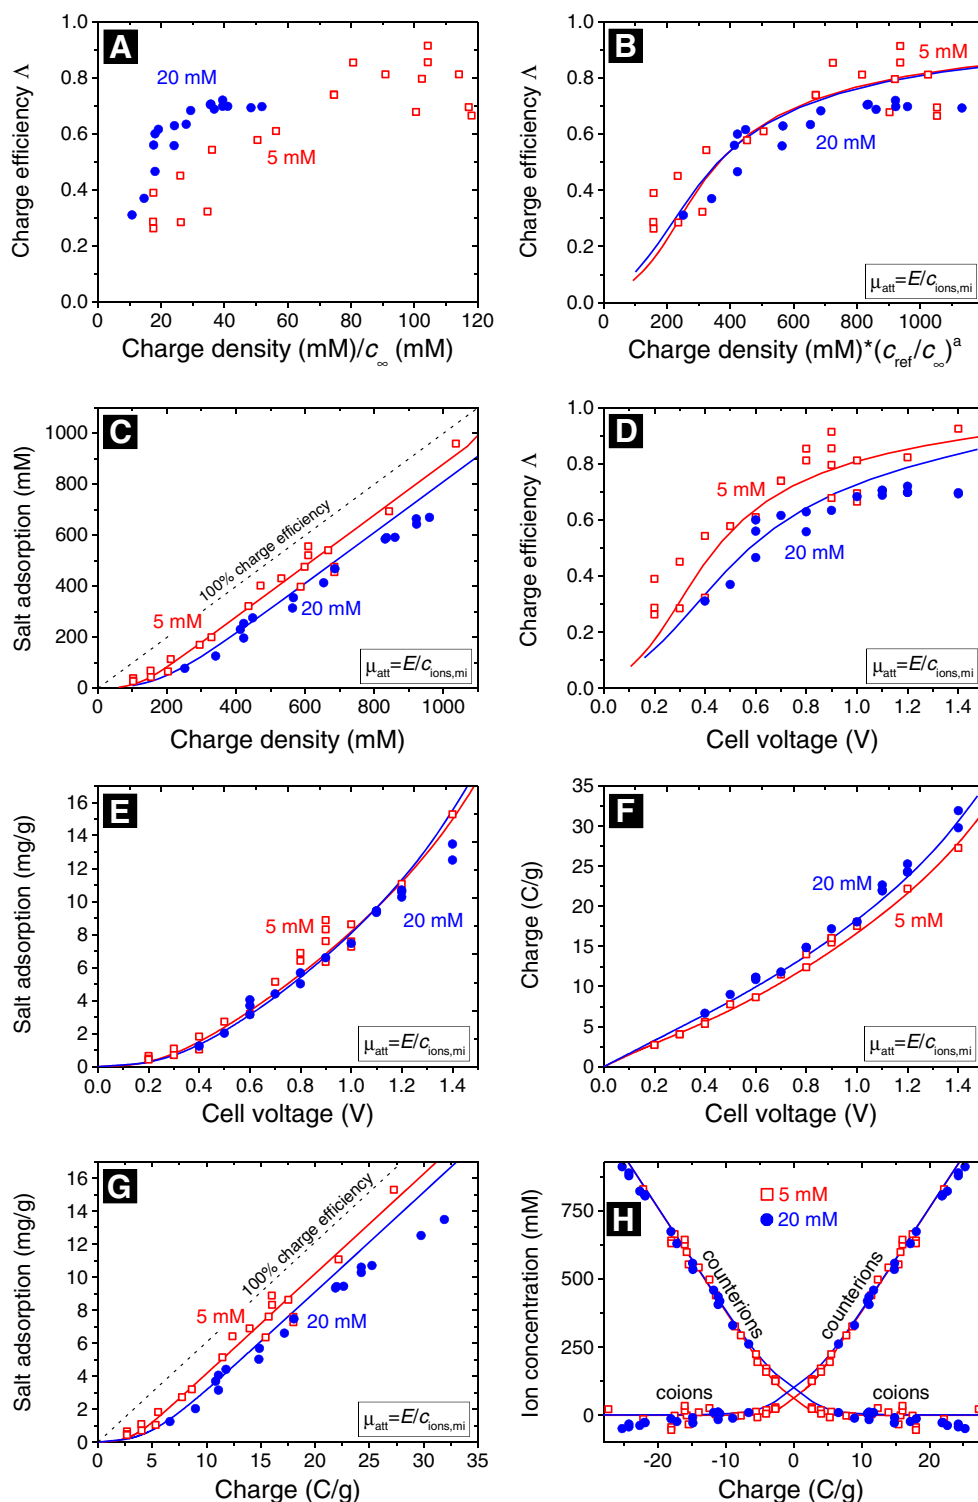

value of E and the micropore volume, v_{mi} ; see Eqs. 11 and 12. The deviation from the 100 % *integral* charge efficiency Λ -line (dashed line at an angle of 45°) is larger for 20 mM than for 5 mM.

Note that for both salt concentrations, there is a range where the data run parallel to this line. In this range, beyond

a micropore charge density of ~ 200 mM, the *differential* charge efficiency λ is unity, and if we would stay in this (voltage) range, for each electron transferred between the electrodes, we remove one full salt molecule. The parallelism of these two lines is typical of EQCM response of carbons, observed for moderate charge densities [78]. Figure 3d is the

classical representation of Λ vs. V_{cell} , and we obtain a much better fit than in Fig. 2b in ref. [38], with the influence of the external salinity no longer overpredicted. Furthermore, we reproduce in Fig. 3e–g the direct measurement data of salt adsorption in milligrams per gram and charge in coulombs per gram for this material and find a very good fit of the model to these four datasets (see note 2). In Fig. 3h, we recalculate data and theory to the counterion and co-ion concentrations in the pores, a graph similar to one by Oren and Soffer [13] and by Kastening et al. [65, 79]. Analyzing the model results, e.g., for $c_{\infty}=5$ mM, the predicted total ion concentration in the pores increases from a minimum value of $c_{\text{ions,mi}}=120$ mM at zero charge, to about 1 M at $V_{\text{cell}}=1.4$ V.

With a value of $E=300$ kJ mol⁻¹, and at $c_{\infty}=5$ mM, the attraction energy, μ_{att} , is at a maximum of 2.48 kJ at zero charge and decreases steadily with charging to a value of $\mu_{\text{att}}=0.28$ kJ at $V_{\text{cell}}=1.4$ V. The attractive energy inferred from the experimental data using the mD porous electrode model is quantitatively consistent with Eq. 19 from our simple theory of image forces without any fitting parameters. Using $\lambda_p=2$ nm, the experimental value $E=0.3$ kJ M implies $\lambda_B=2.9$ nm, or $\epsilon_p=0.25 \cdot \epsilon_b=20 \cdot \epsilon_0$, which is a realistic value for the micropore permittivity. Admittedly, the quantitative agreement may be fortuitous and could mask other effects, such as ion adsorption equilibria, but it is clear that the overall scale and concentration dependence of the attractive energy are consistent with image forces.

Data at one cell voltage level for a range of salt concentrations ($0.25 \cdot \epsilon_b - 20 \cdot \epsilon_0$ mM NaCl)

Next, we extend the testing of the same improved mD model to a much larger range of NaCl salt concentrations, from 2.5 to 200 mM, all evaluated at 1.2 V of cell voltage; see Fig. 3 of ref. [38] for NaCl salt concentrations ranging from 2.5 to 100 mM. In Fig. 4, this range is extended to 200 mM by including extra unpublished work related to material in refs. [21, 77]. In ref. [38] using the standard mD model, it proved impossible to fit the model to the data for the whole range of salinities, with beyond $c_{\infty}=40$ mM the charge underestimated, and salt adsorption underestimated even more, leading to an underprediction of the charge efficiency; see the line denoted “ $\mu_{\text{att}}=\text{constant}$ ” in Fig. 4b. The experimental observation that the salt adsorption does not change much with external salt concentration up to 100 mM could not be reproduced at all. However, with the modification to make μ_{att} inversely proportional to $c_{\text{ions,mi}}$, a very good fit to the data is now obtained, both for charge and for salt adsorption, as we can observe in Fig. 4a. Figure 4b presents the results of the charge efficiency Λ , which is the ratio of salt adsorption to

charge (including Faraday’s number to convert charge to moles per gram), and as can be observed, the improved mD model using $\mu_{\text{att}}=E/c_{\text{ions,mi}}$ shows a much better fit to the data than the standard mD model which assumes μ_{att} to be constant.

Data for unequal electrode mass (5 and 20 mM NaCl)

Data for NaCl adsorption in asymmetric CDI systems were presented by Porada et al. [39]. That work is based on varying the electrode mass ratio, i.e., by placing on one side of the spacer channel two or three electrodes on top of one another. In this way, a cell is constructed which has two times, or three times, the anode mass relative to cathode mass, or vice versa. In Fig. 5, we present the data for charge efficiency, Λ , defined as salt adsorption by the cell pair divided by charge, vs. the mCmA ratio, which is the mass ratio of cathode to anode. Here, data are presented at a cell voltage of $V_{\text{cell}}=1.0$ V and a salt concentration of 5 and 20 mM, like Fig. 3c in ref. [39]. Comparing with the fit obtained by Porada et al. using a constant value of μ_{att} (dashed lines in Fig. 5), a significantly improved fit is now achieved.

Analysis of data for adsorption of salt in uncharged carbon—measuring μ_{att}

A crucial assumption in the mD models is the existence of an attractive energy, μ_{att} , for ions to move into carbon micropores, which we attribute to image forces as a first approximation. The existence of this energy term implies that uncharged carbons must adsorb some salt, as known from refs. [49, 50] and references therein, and as can also be inferred from refs. [65, 80]. In the present section, we show results of the measurement of μ_{att} by directly measuring the adsorption of NaCl in an activated carbon powder (Kuraray YP50-F, Kuraray Chemical, Osaka, Japan). This carbon is mainly microporous with 0.64 mL/g in the pore size range of <2 nm and 0.1 mL/g mesopores [34].

The carbon powder was washed various times in distilled water and filtered, to remove any possible ionic/metallic constituents of the carbon, and was finally dried in an oven at 100 °C. A volume of water V with predefined NaCl concentration was mixed with various amounts of carbon (mass m) in sealed flasks. These flasks were gently shaken for 48 h. The carbon/water slurry is pressed through a Millipore Millex-LCR filter (Millipore, MA, USA), and the supernatant was analyzed to measure the decrease in salt concentration, from which we calculate the salt adsorption. Note that both the initial and final salt concentrations in the water are analyzed in the same analysis program, and the difference is used to calculate salt adsorption. The pH that initially was around pH 6–7 increased to values of pH~9 after soaking with carbon.

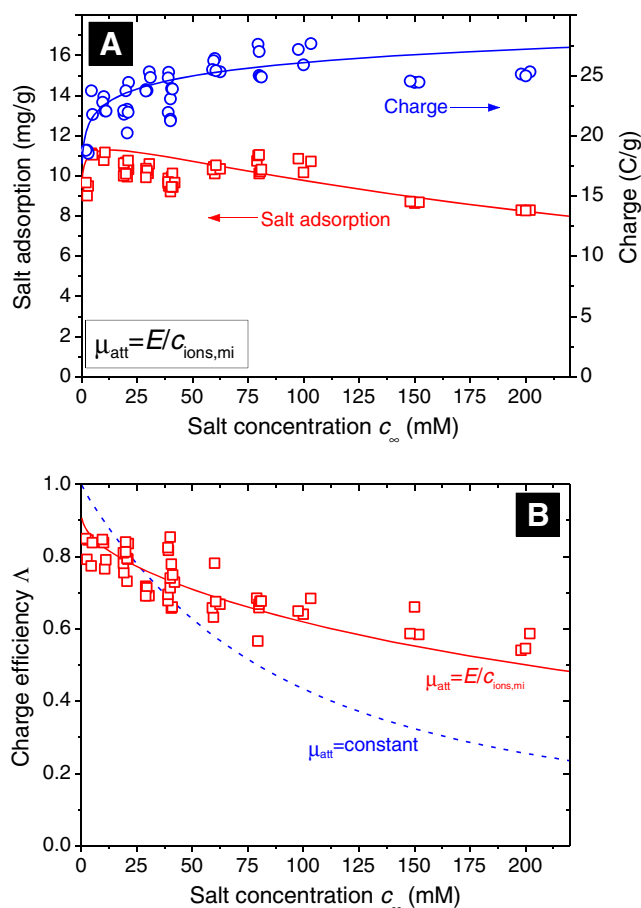


Fig. 4 **a** Salt adsorption and charge density, and **b** charge efficiency Λ , for CDI in a range of NaCl salt concentrations (2.5–200 mM) at $V_{cell} = 1.2$ V. Both in **a** and **b**, solid lines denote calculation results of the improved mD model, while in **b**, the dashed line is based on the standard mD model

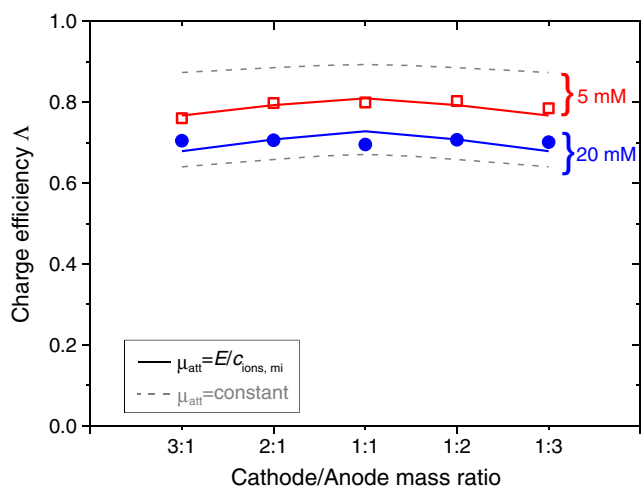


Fig. 5 Charge efficiency for CDI at unequal mass ratio cathode to anode ($V_{cell} = 1.0$ V). Dashed lines show prediction using a fixed μ_{att} in the standard mD model, while the solid lines show results for the improved mD model where $\mu_{att} = E/c_{ions,mi}$

By ion chromatography (IC), we measure the Cl^- content of the supernatant (see note 3).

The excess salt adsorption is calculated from the measured decrease in Cl^- concentration, Δc , in the supernatant (relative to that in the initial solution) according to $n_{salt,exc} = V/m \cdot \Delta c$ in moles per gram, which we multiply by $v_{mi} = 0.64$ mL/g to obtain an estimate for the excess salt concentration in the pores, c_{exc} . The excess concentration is plotted against the final (after equilibration) salt concentration (again based on the measured Cl^- concentration) in Fig. 6. By “excess concentration” we mean the difference in concentration in the carbon pores, relative to that outside the carbon particles.

As Fig. 6 demonstrates, the measured excess salt adsorption, c_{exc} , as a function of the external salt concentration, c_{∞} , has a broad maximum in the range from 5 to 100 mM, and beyond that, c_{exc} decreases gradually. The measured excess adsorption of around 55 mM recalculates to a salt adsorption of about 2 mg/g. This number is about a factor of 10 lower than values obtained for mixed adsorbents (some containing activated carbon) reported in ref. [81] and a factor 5 lower than values for alkali and acid adsorption reported by Garten and Weiss [50]. The standard mD model assuming a constant μ_{att} does not describe these data at all. In Fig. 6, a line is plotted for $\mu_{att} = 0.4$ kT, much lower than the values for μ_{att} used by us in an earlier work, which were mostly around $\mu_{att} = 1.5$ kT, but even this low value of $\mu_{att} = 0.4$ kT results in a model prediction which significantly overpredicts c_{exc} at salt concentrations beyond $c_{\infty} = 100$ mM. Thus, taking a constant value of μ_{att} does not describe data at all. The improved mD model using $\mu_{att} = E/c_{ions,mi}$ (upper curved line) works much better and more closely describes the fact that c_{exc} levels off with

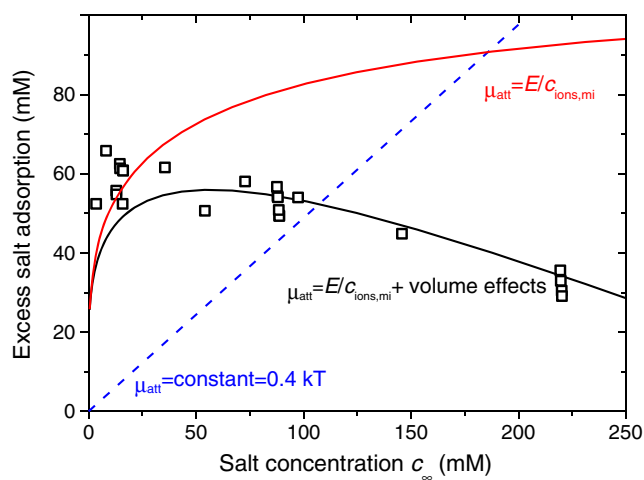


Fig. 6 Excess adsorption of NaCl in uncharged carbon as function of external salt concentration, c_{∞} . Straight dashed line based on standard mD model (constant $\mu_{att} = 0.4$ kT), upper curved line based on the improved mD model, and lower curved line for extended model including ion volume effects

increasing c_{∞} . However, it still does not describe the fact that a maximum develops, and that at high c_{∞} , the excess adsorption decreases again. To account for this nonmonotonic effect, we include an ion volume correction according to a modified Carnahan-Starling equation of state [44, 45, 47, 63]. For an ion, because of its volume, there is an excess, volumetric contribution to the ion chemical potential, both in the external solution and in the micropores. This excess contribution is calculated from

$$\mu_{\text{exc}} = \phi \cdot (8 - 9 \cdot \phi + 3 \cdot \phi^2) \cdot (1 - \phi)^{-3} = (3 - \phi) \cdot (1 - \phi)^{-3} - 3 \quad (20)$$

where ϕ is the volume fraction of all ions together. In an external solution, to calculate $\mu_{\text{exc}}^{\infty}$, we use $\phi = 2 \cdot v_{\text{ion}} \cdot c_{\infty}$, where v_{ion} is the ion volume ($v_{\text{ion}} = \pi/6 \cdot d_{\text{ion}}^3$, where d_{ion} is the ion size), and the factor 2 stems from the fact that a salt molecule consists of two ions; while in the carbon pores, to calculate $\mu_{\text{exc}}^{\text{pore}}$, we replace in Eq. 20 ϕ by ϕ_{eff} , for which we use the empirical expression $\phi_{\text{eff}} = v \cdot c_{\text{ions,mi}} + \alpha \cdot d_{\text{ion}}/d_{\text{pore}}$, derived from fitting calculation results of the average density of spherical particles in a planar slit based on a weighted density approximation (van Soestbergen (2013) personal communication, [82]), where α is an empirical correction factor of $\alpha = 0.145$ and where d_{pore} is the pore width. For a very large pore, or for very small ions, the correction factor tends to zero.

The excess salt concentration as plotted in Fig. 6 is given by $c_{\text{exc}} = 1/2 \cdot c_{\text{ions,mi}} - c_{\infty}$ and is calculated via

$$c_{\text{ions,mi}} = 2 \cdot c_{\infty} \cdot \exp(\mu_{\text{att}} + \mu_{\text{exc}}^{\infty} - \mu_{\text{exc}}^{\text{pore}}). \quad (21)$$

Equations 20 and 21 present a self-consistent set of equations that can be solved to generate the curves in Fig. 6. To calculate the lines for the improved mD model without ion volume effects, ϕ is set to zero.

To obtain the best fit in Fig. 6, we use $E = 220 \text{ kT mol/m}^3$, and for the ion and pore sizes, we use $d_{\text{ion}} = 0.5 \text{ nm}$ and $d_{\text{pore}} = 2.5 \text{ nm}$. This pore size is representative for the microporous material used, while the E value is close to that used in the previous sections. For the model including volume effects, the derived values for the term μ_{att} decrease from $\mu_{\text{att}} = 2.47 \text{ kT}$ at $c_{\infty} = 5 \text{ mM NaCl}$ to $\mu_{\text{att}} = 0.46 \text{ kT}$ at 200 mM . The volume exclusion term, $\mu_{\text{exc}}^{\text{pore}} - \mu_{\text{exc}}^{\infty}$, is quite independent of c_{∞} at around 0.28 kT . As can be observed in Fig. 6, beyond 25 mM , a good fit is now obtained.

Thus, we conclude that the analysis presented in this section underpins the fact that uncharged carbon absorbs salt, and that the data are well described by a model using an attractive energy term μ_{att} inversely proportional to the total ion concentration to account for image forces, in combination with a correction to include ion volume effects as an extra repelling force which counteracts ion adsorption at high salt concentrations.

Conclusions

We have demonstrated that in order to describe charge and salt adsorption in porous carbon electrodes for CDI, the predictive power of the modified Donnan model can be significantly increased by assuming that the ion attractive energy μ_{att} is no longer a fixed constant, but is inversely related to the total ion concentration in the pores. In this way, the anomaly of predicted extremely high salt adsorptions in carbons in contact with high salt solutions, such as seawater, is resolved. Whereas in the standard mD model, using as an example a constant value of $\mu_{\text{att}} = 2.0 \text{ kT}$, the excess adsorption of salt from water of a salinity of 0.5 M (sea water) into uncharged carbon is predicted to be 3.19 M , in the improved mD model, with $E = 300 \text{ kT mol/m}^3$, this excess adsorption is only 0.13 M , a much more realistic value. Actually, extrapolation of data presented in Fig. 6 suggests that in a 0.5 M salt solution, the effect of ion volume exclusion may be high enough that instead of an excess adsorption, we have less salt in the pores than in the outside solution. The improved Donnan model not only has relevance for modeling the EDL structure in porous electrodes for CDI, but also for membrane CDI [83–86], salinity gradient energy [40, 55], and for energy harvesting from treating CO_2 containing power plant flue gas [87, 88].

This work also highlights for the first time the important role of electrostatic image forces in porous electrodes, which cannot be described by classical mean-field theories. We propose a simple approximation that works very well for the data presented here. This result invites further systematic testing and more detailed theory. The theory can be extended for larger pores with nonuniform ion densities, and by making use of more accurate models of the Stern layer, including its dielectric response and specific adsorption of ions. Unlike the situation for biological molecules [89] and ion channels [90], where image forces are repulsive due to the low dielectric constant, metallic porous electrodes generally exert attractive image forces on ions that contribute to salt adsorption, even at zero applied voltage.

Notes

- Note that for a symmetric 1:1 salt, and for a symmetric electrode, there is no effect of explicitly considering the two values of μ_{att} to be different, as long as their average is same. When considering $\mu_{\text{att,Na}}$ and $\mu_{\text{att,Cl}}$ to be different, still the same model output (charge and salt adsorption versus cell voltage) is generated, and only the individual Donnan potentials change in both electrodes—one up, one down—with their sum remaining the same. However, for asymmetric electrodes, or asymmetric salts (such as CaCl_2), and for salt mixtures [25], there is an effect of the individual values of μ_{att} on the measurable performance of a CDI cell. Of course, it must be the case that μ_{att} differs between different ion types as it is known that specific adsorption of ions increases with

their size, which is correlated with their lower solvation ability: from F^- to I^- , and from Li^+ to Cs^+ [91, 92].

- 2 Note that to analyze the data of ref. [16], as presented in Fig. 2, the mass as assumed erroneously in ref. [16] to be 10.6 g must be corrected to a mass of 8.5 g, and thus the reported salt adsorption and charge in ref. [16] is multiplied by 10.6/8.5. Note that in ref. [38], a correction to 8.0 g was assumed in Fig. 2 there.
- 3 Also the Na^+ concentration was measured in all samples, using inductively coupled plasma mass spectrometry. Analysis of the electrolyte solution prior to contacting with carbon gave a perfect match of Na^+ concentration to Cl^- concentration. However, analysis of the supernatant that had been in contact with the carbon quite consistently gave a lower Cl^- concentration than Na^+ concentration, by 1–6 mM (thus more Cl^- adsorption in the carbon), in line with the higher reported anion vs. cation adsorption for carbons activated beyond 600 °C [50], and for mixed adsorbent samples reported in Fig. 2 of ref. [81].

Acknowledgments Part of this work was performed in the cooperation framework of Wetsus, Centre of Excellence for Sustainable Water Technology (www.wetsus.nl). Wetsus is co-funded by the Dutch Ministry of Economic Affairs and Ministry of Infrastructure and Environment, the European Union Regional Development Fund, the Province of Fryslân, and the Northern Netherlands Provinces. The authors like to thank the participants of the research theme Capacitive Deionization for fruitful discussions and financial support. We thank Michiel van Soestbergen for providing unpublished theoretical results used in section “Analysis of data for adsorption of salt in uncharged carbon—measuring μ_{att} ”.

References

1. Arnold BB, Murphy GW (1961) *J Phys Chem* 65:135–138
2. Farmer JC, Fix DV, Mack GV, Pekala RW, Poco JF (1996) *J Electrochem Soc* 143:159–169
3. Johnson AM, Newman J (1971) *J Electrochem Soc* 118:510–517
4. Soffer A, Folman M (1972) *J Electroanal Chem Interface Electrochem* 38:25–43
5. Suss ME, Baumann TF, Bourcier WL, Spadaccini CM, Rose KA, Santiago JG, Stadermann M (2012) *Energy Environ Sci* 5:9511–9519
6. Rica RA, Ziano R, Salerno D, Mantegazza F, Brogioli D (2012) *Phys Rev Lett* 109:156103
7. Porada S, Zhao R, van der Wal A, Presser V, Biesheuvel PM (2013) *Prog Mater Sci* 58:1388–1442
8. Jeon S-I, Park H-R, Yeo J-G, Yang S, Cho CH, Han MH, Kim D-K (2013) *Energy Environ Sci* 6:1471–1475
9. Jande YAC, Kim WS (2013) *Desalination* 329:29–34
10. Jande YAC, Kim WS (2013) *Sep Purif Technol* 115:224–230
11. Garcia-Quismondo E, Gomez R, Vaquero F, Cudero AL, Palma J, Anderson MA (2013) *Phys Chem Chem Phys* 15:7648–7656
12. Wang G, Qian B, Dong Q, Yang J, Zhao Z, Qiu J (2013) *Sep Purif Technol* 103:216–221
13. Oren Y, Soffer A (1983) *J Appl Electrochem* 13:473–487
14. Levi MD, Salitra G, Levy N, Aurbach D, Maier J (2009) *Nat Mater* 8: 872–875
15. Avraham E, Bouhadana Y, Soffer A, Aurbach D (2009) *J Electrochem Soc* 156:95–99
16. Zhao R, Biesheuvel PM, Miedema H, Bruning H, van der Wal A (2010) *J Phys Chem Lett* 1:205–210
17. Levi MD, Levy N, Sigalov S, Salitra G, Aurbach D, Maier J (2010) *J Am Chem Soc* 132:13220–13222
18. Kastening B, Heins M (2001) *Phys Chem Chem Phys* 3:372–373
19. Han L, Karthikeyan KG, Anderson MA, Gregory K, Wouters JJ, Abdel-Wahab A (2013) *Electrochim Acta* 90:573–581
20. Mossad M, Zou L (2013) *Chem Eng J* 223:704–713
21. Zhao R, Biesheuvel PM, Van der Wal A (2012) *Energy Environ Sci* 5:9520–9527
22. Wu P, Huang J, Meunier V, Sumpster BG, Qiao R (2012) *J Phys Chem Lett* 3:1732–1737
23. Bazant MZ, Thornton K, Ajdari A (2004) *Phys Rev E* 70:021506
24. Biesheuvel PM, Bazant MZ (2010) *Phys Rev E* 81:031502
25. Zhao R, van Soestbergen M, Rijnaarts HHM, van der Wal A, Bazant MZ, Biesheuvel PM (2012) *J Colloid Interface Sci* 384:38–44
26. Yang K-L, Ying T-Y, Yiaccoumi S, Tsouris C, Vittoratos ES (2001) *Langmuir* 17:1961–1969
27. Gabelich CJ, Tran TD, Suffet IH (2002) *Environ Sci Technol* 36: 3010–3019
28. Hou C-H, Liang C, Yiaccoumi S, Dai S, Tsouris C (2006) *J Colloid Interface Sci* 302:54–61
29. Xu P, Drewes JE, Heil D, Wang G (2008) *Water Res* 42:2605–2617
30. Li L, Zou L, Song H, Morris G (2009) *Carbon* 47:775–781
31. Gabelich CJ, Xu P, Cohen Y (2010) *Sustain Sci Eng* 2:295–326
32. Tsouris C, Mayes R, Kiggans J, Sharma K, Yiaccoumi S, DePaoli D, Dai S (2011) *Environ Sci Technol* 45:10243–10249
33. Porada S, Weinstein L, Dash R, van der Wal A, Bryjak M, Gogotsi Y, Biesheuvel PM (2012) *ACS Appl Mater Interfaces* 4:1194–1199
34. Porada S, Borchardt L, Oschatz M, Bryjak M, Atchison J, Keesman KJ, Kaskel S, Biesheuvel M, Presser V (2013) *Energy Environ Sci* 6: 3700–3712
35. Lin C, Ritter JA, Popov BN (1999) *J Electrochem Soc* 146:3639–3643
36. Kim T, Yoon J (2013) *J Electroanal Chem* 704:169–174
37. Sharma K, Mayes RT, Kiggans JO Jr, Yiaccoumi S, Gabitto J, DePaoli DW, Dai S, Tsouris C (2013) *Sep Purif Technol* 116:206–213
38. Biesheuvel PM, Zhao R, Porada S, van der Wal A (2011) *J Colloid Interface Sci* 360:239–248
39. Porada S, Bryjak M, van der Wal A, Biesheuvel PM (2012) *Electrochim Acta* 75:148–156
40. Rica RA, Brogioli D, Ziano R, Salerno D, Mantegazza F (2012) *J Phys Chem C* 116:16934–16938
41. Porada S, Sales BB, Hamelers HVM, Biesheuvel PM (2012) *J Phys Chem Lett* 3:1613–1618
42. Andersen MB, van Soestbergen M, Mani A, Bruus H, Biesheuvel PM, Bazant MZ (2012) *Phys Rev Lett* 109:108301
43. Galama AH, Post JW, Cohen Stuart MA, Biesheuvel PM (2013) *J Membr Sci* 442:131–139
44. Biesheuvel PM, de Vos WM, Amoskov VM (2008) *Macromolecules* 41:6254–6259
45. de Vos WM, Biesheuvel PM, de Keizer A, Kleijn JM, Cohen Stuart MA (2009) *Langmuir* 25:9252–9261
46. Biesheuvel PM (2004) *J Phys Condens Matter* 16:L499–L504
47. Spruijt E, Biesheuvel PM (2014) *J Phys Condens Matter* 26:075101
48. Huang J, Qiao R, Feng G, Sumpster BG, Meunier V (2013) *Modern Theories of Carbon-Based Electrochemical Capacitors, in Supercapacitors*. Wiley, New York, pp 167–206
49. Garten VA, Weiss DE (1955) *Aust J Chem* 8:68–95
50. Garten VA, Weiss DE (1957) *Rev Pure Appl Chem* 7:69–122
51. Attard P, Mitchell DJ, Ninham BW (1988) *J Chem Phys* 89:4358–4367
52. Skinner B, Loth MS, Shklovskii BI (2010) *Phys Rev Lett* 104: 128302
53. Biesheuvel PM, Fu YQ, Bazant MZ (2011) *Phys Rev E* 83:061507
54. Biesheuvel PM, Fu Y, Bazant MZ (2012) *Russ J Electrochem* 48: 580–592

55. Rica RA, Ziano R, Salerno D, Mantegazza F, Bazant MZ, Brogioli D (2013) *Electrochim Acta* 92:304–314
56. Hou C-H, Patricia T-S, Yiacoumi S, Tsouris C (2008) *J Chem Phys* 129:224703–224709
57. Feng G, Qiao R, Huang J, Sumpster BG, Meunier V (2010) *ACS Nano* 4:2382–2390
58. Bonthuis DJ, Gekle S, Netz RR (2011) *Phys Rev Lett* 107:166102
59. Feng G, Cummings PT (2011) *J Phys Chem Lett* 2:2859–2864
60. Kondrat S, Komyshv A (2011) *J Phys Condens Matter* 23:022201
61. Jadhao V, Solis FJ, de la Cruz MO (2013) *J Chem Phys* 138:054119-13
62. Jiménez ML, Fernández MM, Ahualli S, Iglesias G, Delgado AV (2013) *J Colloid Interface Sci* 402:340–349
63. Wang H, Thiele A, Pilon L (2013) *J Phys Chem C* 117:18286–18297
64. Kobrak MN (2013) *J Phys Condens Matter* 25:095006
65. Kastening B, Heins M (2005) *Electrochim Acta* 50:2487–2498
66. Suss, M.E., T.F., Baumann, M.A. Worsley, K.A. Rose, T.F. Jaramillo, M. Stadermann, J.G. Santiago (2013) *J Power Sources* 241: 266–273
67. Grahame DC (1947) *Chem Rev* 41:441–501
68. Bazant MZ, Chu KT, Bayly BJ (2005) *SIAM J Appl Math* 65:1463–1484
69. Kalluri RK, Biener MM, Suss ME, Merrill MD, Stadermann M, Santiago JG, Baumann TF, Biener J, Striolo A (2013) *Phys Chem Chem Phys* 15:2309–2320
70. Andersen PS, Fuchs M (1975) *Biophys J* 15:795–830
71. Grosberg AY, Nguyen TT, Shklovskii BI (2002) *Rev Mod Phys* 74: 329–345
72. Santangelo CD (2006) *Phys Rev E* 73:041512
73. Hatlo MM, Lue L (2010) *EPL Europhys Lett* 89:25002
74. Bazant MZ, Storey BD, Komyshv AA (2011) *Phys Rev Lett* 106: 046102
75. Jackson, J.D. (1975) *Classical electrodynamics*. Second edition ed: Wiley. 848
76. Zhao R, Satpradit O, Rijnaarts HHM, Biesheuvel PM, van der Wal A (2013) *Water Res* 47:1941–1952
77. Zhao R, Porada S, Biesheuvel PM, van der Wal A (2013) *Desalination* 330:35–41
78. Levi MD, Sigalov S, Aurbach D, Daikhin L (2013) *J Phys Chem C* 117:14876–14889
79. Müller M, Kastening B (1994) *J Electroanal Chem* 374:149–158
80. Gupta VK, Pathania D, Sharma S, Singh P (2013) *J Colloid Interface Sci* 401:125–132
81. Aghakhani A, Mousavi SF, Mostafazadeh-Fard B, Rostamian R, Seraji M (2011) *Desalination* 275:217–223
82. Tarazona P (1985) *Phys Rev A* 31:2672–2679
83. Dlugolecki P, van der Wal A (2013) *Environ Sci Technol* 47:4904–4910
84. Liang P, Yuan L, Yang X, Zhou S, Huang X (2013) *Water Res* 47: 2523–2530
85. Kim Y-J, Kim J-H, Choi J-H (2013) *J Membr Sci* 429:52–57
86. Yeo J-H, Choi J-H (2013) *Desalination* 320:10–16
87. Hamelers, H.V.M., O. Schaetzle, J.M. Paz-García, P.M. Biesheuvel, and C.J.N. Buisman (2014) *Environ Sci Technol Lett* 1:31–35
88. Paz-Garcia, J.M., O. Schaetzle, P.M. Biesheuvel, H.V.M. Hamelers (2014) *J Colloid Interface Sci* 418:200–207
89. Grochowski P, Trylska J (2008) *Biopolymers* 89:93–113
90. Levitt DG (1986) *Annu Rev Biophys Biophys Chem* 15:29–57
91. Levi MD, Sigalov S, Salitra G, Aurbach D, Maier J (2011) *ChemPhysChem* 12:854–862
92. Levi MD, Sigalov S, Salitra G, Elazari R, Aurbach D (2011) *J Phys Chem Lett* 2:120–124